



**HAL**  
open science

## Normalised model-based processing diagrams for additive manufacturing of soft magnetic materials

Yuyang Li, Alejandro Ospina, Meher Zaied, Jérôme Favergeon, Nour-Eddine Fenineche, Thierry Baffie, Salima Bouvier

► **To cite this version:**

Yuyang Li, Alejandro Ospina, Meher Zaied, Jérôme Favergeon, Nour-Eddine Fenineche, et al.. Normalised model-based processing diagrams for additive manufacturing of soft magnetic materials. 2ndes journées du GDR ALMA, Jun 2023, Rouen, France. 2023. hal-04290306

**HAL Id: hal-04290306**

**<https://utc.hal.science/hal-04290306v1>**

Submitted on 16 Nov 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Normalised model-based processing diagrams for additive manufacturing of soft magnetic materials

Yuyang LI<sup>1</sup>, Alejandro OSPINA VARGAS<sup>1</sup>, Meher ZAIED<sup>2</sup>, Nouredine FENINECHE<sup>2</sup>, Jérôme FAVERGEON<sup>1</sup>, Thierry BAFFIE<sup>3</sup>,  
Salima BOUVIER<sup>1</sup>

<sup>1</sup> Université de technologie de Compiègne, CNRS, Roberval (Mechanics energy and electricity), Centre de recherche Royallieu - CS 60 319 - 60 203 Compiègne Cedex

<sup>2</sup> ICB LERMP5 ICB UMR 6303, CNRS, Univ. Bourgogne Franche-Comté, UTBM, F-90010 Belfort, France

<sup>3</sup> Univ. Grenoble Alpes, CEA, LITEN, F-38000 Grenoble, France

## Introduction

- Laser beam melting (LBM) is an additive manufacturing technique that uses a laser beam to melt powdered materials to produce metal parts.
- Benefits : LBM excels at producing parts with desired magnetic properties, especially in the area of soft magnetic materials such as high silicon steel.
- Goal : Create a concise chart integrating normalized energy density and provide a comprehensive overview of materials and parameters from multiple research articles.

## Normalised process parameters and normalised energy density

**Normalised process parameters :** A global expression of normalized energy, as defined by Thomas, consists of four dimensionless quantities:


- Dimensionless laser power ( $P^* = \frac{AP}{r_B \lambda \Delta T}$ )
- Dimensionless laser scanning speed ( $v^* = \frac{vr_B}{\alpha}$ )
- Dimensionless hatch distance ( $h^* = \frac{h}{r_B}$ )
- Dimensionless layer thickness ( $l^* = \frac{2l}{r_B}$ )

where  $A$  is the powder absorptivity,  $\lambda$  is the thermal conductivity,  $\Delta T$  is the temperature difference between the melting point temperature and the temperature of the base plate,  $\alpha = \frac{\lambda}{\rho c_p}$  is the thermal diffusivity,  $\rho$  is the material density, and  $c_p$  is the material heat capacity.

**Normalised energy density equation:**

$$E_0^* = \frac{P^*}{v^* h^* l^*} = \left( \frac{P}{2vhl} \right) \left( \frac{A}{2\rho c_p \Delta T} \right)$$


The dimensionless parameter  $E_0^*$  is the average laser energy applied to the powder bed per volume of material and corresponds to the dashed lines in the diagram.

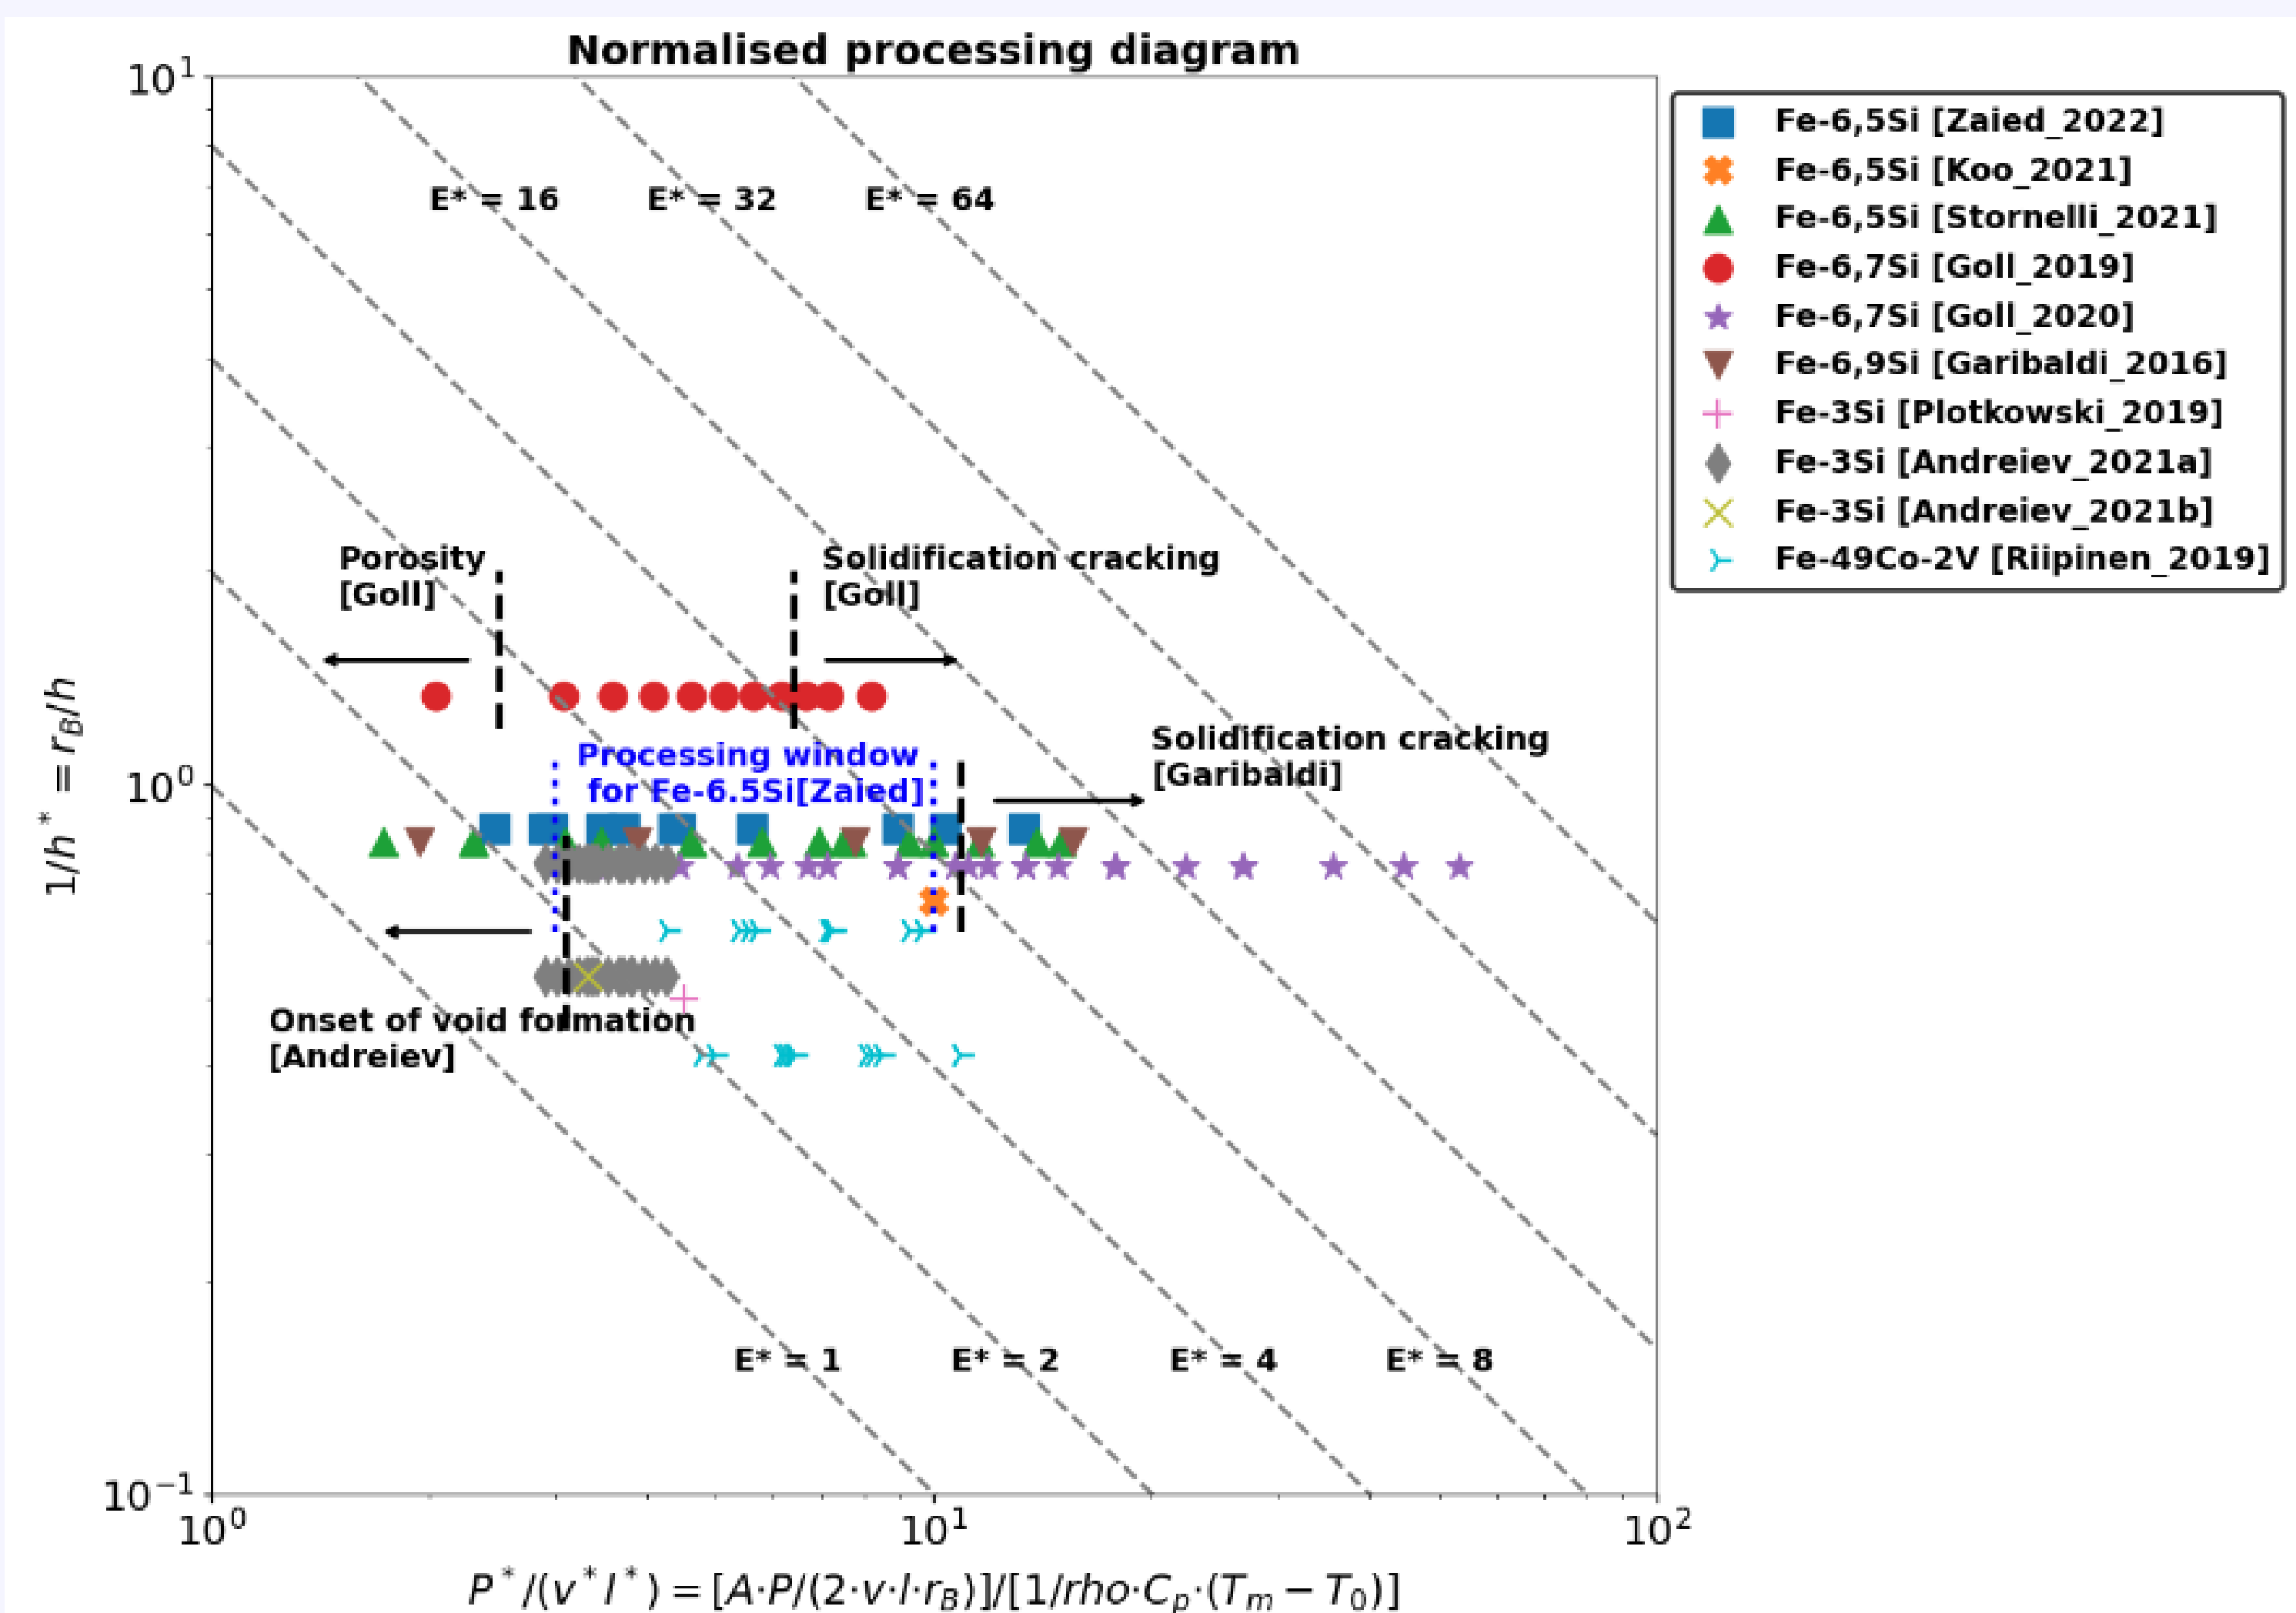

## Evaluation of Density and Porosity

By incorporating density into the normalized processing diagram, a clear correlation can be established between the energy input delivered by the laser and the resulting density of the component. The diagram is structured into three distinct regions based on the density of the components:

- **Region I** corresponds to incomplete melting of the powder due to insufficient energy input, with large irregularly shaped porosity in the components.
- **Region J** corresponds to a high residual stress in the fully melted layer due to high energy input, with many visible cracks and spherical porosities.
- **Region K** corresponds to a completely dense component with a low defect rate.

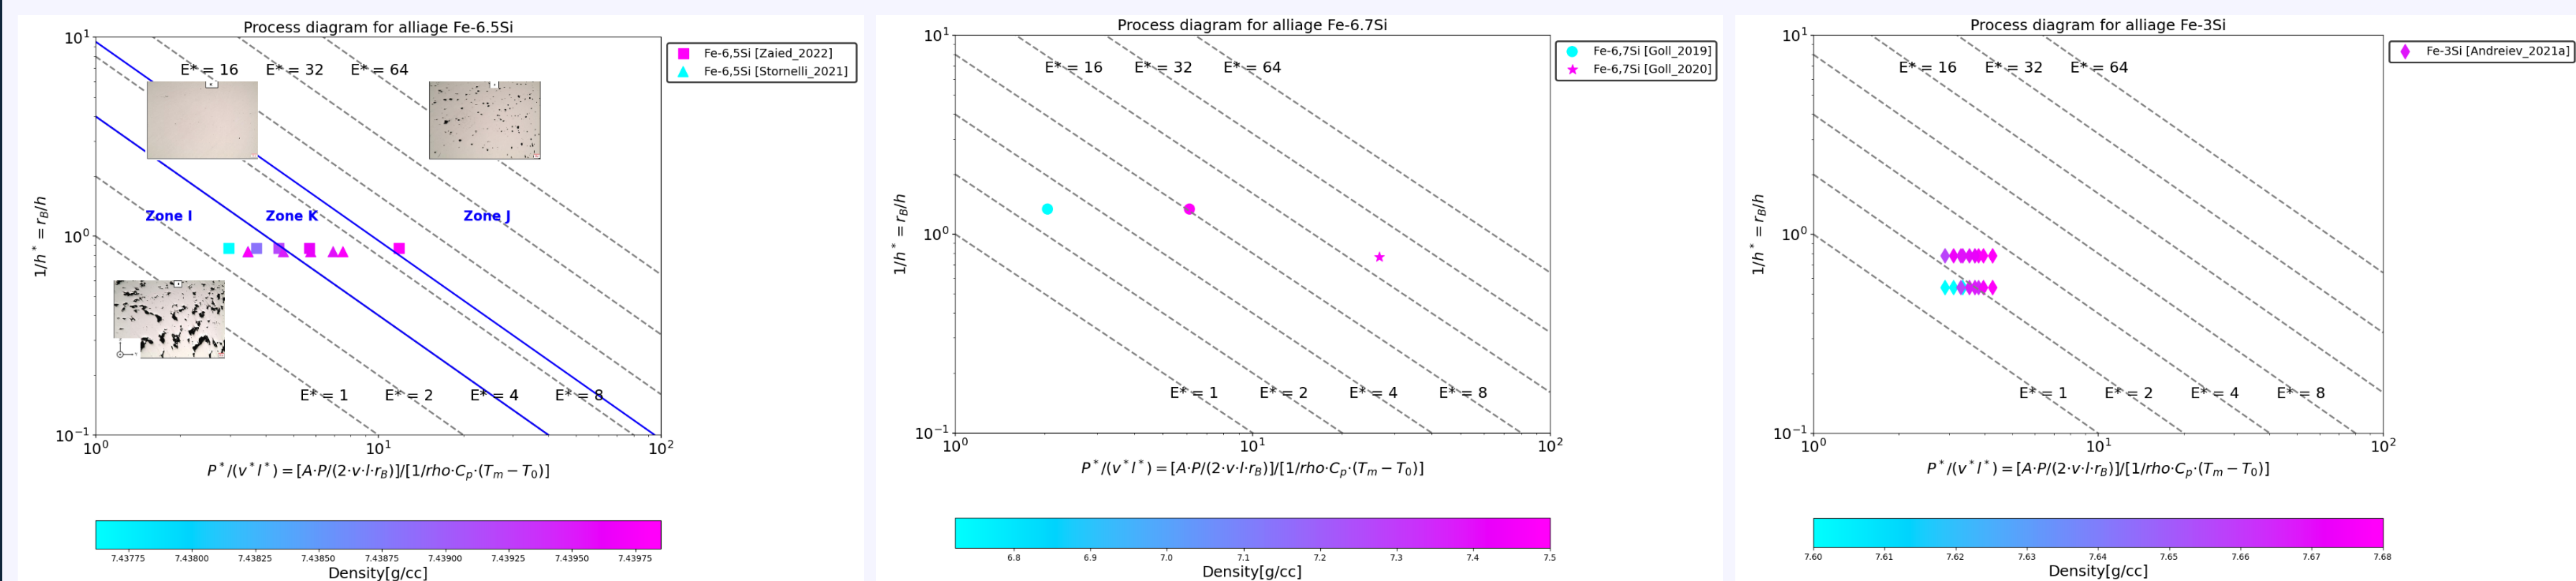

## Conclusion

- The summarized normalized processing diagram provides a practical framework for comparing and categorizing data on alloy materials and processing parameters from existing literature. It offers valuable information for decision-making purposes.
- These diagrams offer insights into how energy input affects the density, porosity, and crack evolution of components. They help identify suitable processing parameters in early research and development programs.

## Acknowledgement

The authors acknowledge the financial support of the IDEX Sorbonne Université in the frame of the french gouvernement program "Investissement d'avenir" as well as the French National Research Agency (ANR) through the FALSTAFF project N° ANR-22-CE08-0029-01.

The authors are also grateful to Roberval-UTC and ICB-LERMP5 technical staff for their support.